



Green synthesis and characterization of iron oxide nanoparticles using *Coriandrum sativum* L. leaf extract

Kuldeep Singh, Dimple Sethi Chopra*, Dhandeep Singh & Nirmal Singh

Department of Pharmaceutical Sciences and Drug Research, Punjabi University, Patiala-147 002, Punjab, India

Received 14 November 2021; revised 18 January 2022

Green nanoparticle synthesis is a promising, eco-friendly and safe approach. In the current study, Iron oxide nanoparticles (FeONPs) were synthesized using aqueous leaf extract of *Coriandrum sativum* L. Further, the characterization of synthesized FeONPs was performed using ultraviolet-visible spectroscopy, transmission electron microscopy (TEM), dynamic light scattering (DLS), vibrating sample magnetometer (VSM) and differential scanning calorimetry (DSC). The surface plasmon resonance effect confirmed the synthesis of FeONPs. Dynamic light scattering (DLS) revealed mean particle size of FeONPs around 163.5 and polydispersity index 0.091 with a zeta potential of -13.8 mV. Differential scanning calorimetry (DSC) exhibited an endothermic peak at 176.91°C . Vibrating sample magnetometer (VSM) analysis showed superparamagnetic properties of iron nanoparticles with a magnetization value of 3.483 emu/g and the results indicated superparamagnetic behavior of prepared iron nanoparticles at room temperature, thus highlighting their potential as magnetically targeted drug delivery system. This biosynthetic method has been proven to be cost-effective, environment friendly and promising for use in biomedical sciences.

Keyword: *Coriandrum sativum* L., Iron Oxide nanoparticle, Superparamagnetic

Nanotechnology is a rapidly expanding field with various application in biological, medicine, and technology. Nanotechnology has advanced in the field of nanoscience over the last 20 years. The synthesizing of nanoparticles (NPs) of different shapes and sizes, as well as their potential applications, are the emphasis of nanotechnology¹. Most experts believe that metal oxide NPs are quite safe for humans and the environment. Metal oxides are commonly used in a variety of fields including environmental research, electrochemistry, and magnetic biology². Iron oxide (FeO) is notable for its biocompatibility and magnetic characteristics and is one of the better metallic NPs for the treatment of certain diseases and infections. Iron oxide nanoparticles (FeONPs) have a wide range of applications, including catalysts, heavy metal adsorption, dyes, and antibiotic degradation³. However, the physical and chemical processes for synthesizing nanoparticles result in clear and distinct nanoparticles, these nanoparticles may not be environment-friendly, and they are highly expensive⁴. Moreover, using the above-mentioned processes to create agglomerates could lead to lower reactivity and stability in these

nanoparticles⁵. In recent years, phytomediated synthesis of nanomaterials has gained popularity since it has various advantages such as being clean, fast, eco-friendly, and non-toxic, and the plant material itself functions as a capping agent⁶. The plant's biological components are integrated with the NPs, which maintains stability and improves shape⁷. Recently, many studies have been conducted for the green synthesis of iron-based nanoparticles from different plant parts such as *Persea americana* rind, *Cynometra ramiflora* fruit extract, *Avicennia marina* flower extract, *Punica granatum* seeds extract etc. for the degradation of different textile dyes⁸⁻¹¹.

The current study attempted to produce iron oxide nanoparticle using *Coriandrum sativum* L. leaf extract. Aqueous ferrous sulphate reactions with *C. sativum* L. leaf extract to produce FeONPs, which are highly stable. The rate of nanoparticle synthesis is extremely fast, which allows the use of crop residues in the synthesis of iron nanoparticles using environmentally benign and more secure methods.

Material and Methods

Materials

Analytical grade Ferrous sulfate heptahydrate was purchased from Himedia Pvt Laboratories (Mumbai) India. The freshly *C. sativum* L. leaves were procured

*Correspondence:

Phone: +91-9814927122 (Mob)

E-mail: dimplechopra1973@gmail.com

from a local market. Further, the sample was authenticated by Dr. Munruchi Kaur, Department of Botany, Punjabi University, Patiala (Punjab), India (account No.: 2021–673).

Preparation of aqueous leaf extract

Fresh *C. sativum* L. leaves were collected and washed with tap water and deionized water. The aqueous extract of leaves was prepared by combining 10 g of plant leaf (cut into small pieces) with 100 mL of deionized water in a 250 mL beaker. After heating the solution to 60°C for 1 h. Then it was cooled and filtered using Whatman No. 1 filter paper. To get a clear solution, the filtrate was centrifuged. A freeze dryer was used to dry this clear extract. This dried powder was passed through 60-mesh sieve and the sample was stored at room temperature in an airtight container for further studies¹².

Biosynthesis of iron oxide nanoparticles

Nanoparticles of iron oxide (FeONPs) have been prepared by addition of *C. sativum* leaf extract dropwise to 0.01 (mM) FeSO₄ in a 100 mL conical flask with constant agitation speed at 1000 rpm. The reaction mixture was agitated for 15 min at 30°C using a magnetic stirrer¹³. The prepared iron oxide nanoparticles (FeONPs) then separated at 15000 rpm for 20 min by centrifugation. The supernatant was discarded and the pellet was washed by triple distilled water and centrifuged several times to purify it. The iron oxide nanoparticles were freeze-dried for 24 h at –78°C with a pressure of 10 Pa. The black pellet was dried and preserved for future research.

Characterization of synthesized FeONPs

A UV-vis spectrophotometer (Shimadzu UV 2450) was used to confirm the synthesis of FeONPs. To determine the size, shape, and elemental composition of FeONPs were using TEM (JEM-1200 Ex, Joel, Japan). It was found that Dynamic light scattering (DLS) was able to estimate the average size, zeta potential and poly dispersity index (PDI) of the synthesized FeONPs (Malvern Instruments Ltd., Malvern, UK) used water as a solvent. The magnetic property of the synthesized FeONPs was determined by drying the nanoparticles to a fine powder. The powdered material was analyzed on a Microsense VSM at the room temperature. Furthermore, the thermal behaviour of a surface capped FeONPs was investigation with DSC (Melter Toledo, DSC 3 star system).

Results and Discussion

Biological synthesis and characterization of FeONPs

FeONPs were prepared using a green approach with *C. sativum* leaf extract in this study. Generally, the leaves of *C. sativum* are high in polyphenol derivatives. The addition of *C. sativum* leaf extract with ferrous sulphate immediate changed in the colour of reaction mixture from brownish to black colour. This colour change suggested a reduction of Fe⁺² ions to zero-valent iron (Fig. 1). The reaction mixture's colour shift resulted in the activation of surface plasmon vibrations from NPs. UV-vis spectroscopy was used to monitor the reduction of Fe⁺² ions in the aqueous extract of *C. sativum* leaf extract.

The formation of iron oxide nanoparticles has indicated by the presence of a strong peak at 225 nm (Fig. 2)¹⁴. FeONPs synthesized using Musa ornate flower sheath extract¹⁵ and *Azadirachta indica*¹⁶ leaf extract are in good agreement with proceeding study. The reduction of iron oxide nanoparticles by *C. sativum* L. extract was confirmed by the presence of appropriate surface plasmon resonance (SPR) with high band intensities and peaks in the visible spectrum¹⁷.

According to DLS study, the mean particle size of the iron oxide nanoparticles was around 163.5 nm (Fig. 3A) due to the increased interfacial surface area. The Polydispersity Index (PDI) has also used to attain information on the size distribution and homogeneity of nanoformulations. The negative charge of zeta potential value was –13.0 mV¹⁸. Which proven moderately stable of the iron nanoparticles (Fig. 3B). The zeta potential indicates the stability of nanoformulations, and a negative value indicates that particle aggregation in the continuous phase has decreased¹⁹. The negative value of iron oxide nanoparticles supports the conjugation of polyphenolic compounds kaempferol, 40-O mequercetin quercetin, 30-O mequercetin, acacetin, vanillic acid, and trans-ferulic acid on the surface of iron oxide nanoparticles²⁰.

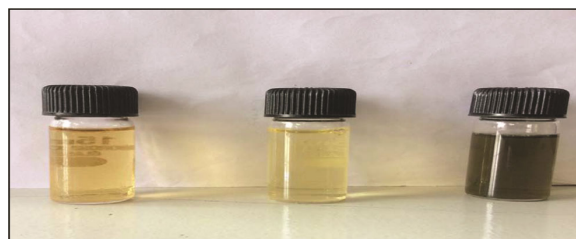


Fig. 1 — (A) *C. sativum* leaf extract; (B) 0.01M ferrous sulphate; and (C) Synthesized iron oxide nanoparticles

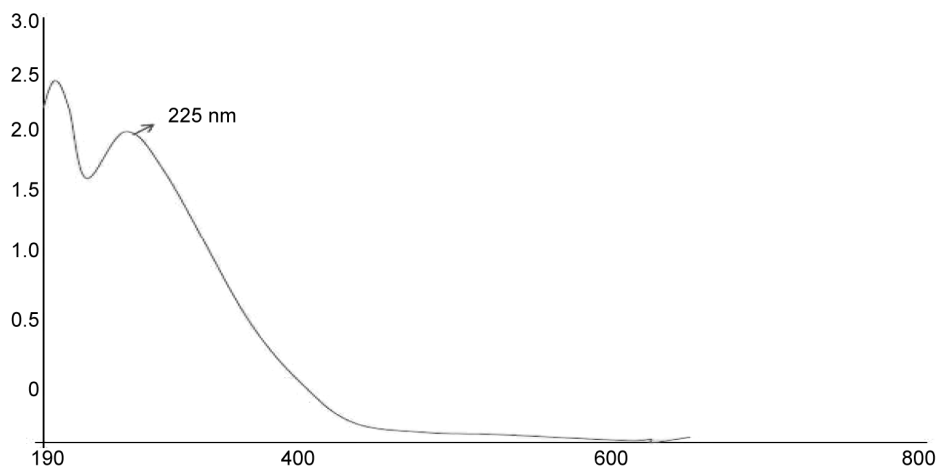


Fig. 2 — UV-vis spectrum image of synthesized iron oxide nanoparticles

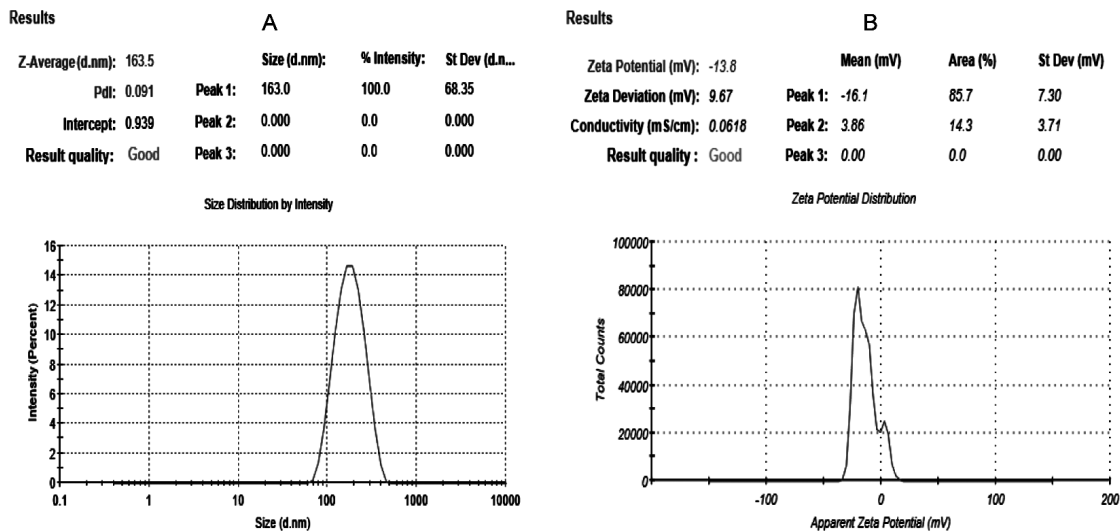


Fig. 3 — (A) Mean particle size; and (B) Zeta potential of optimized iron oxide nanoparticles

The size and surface morphology of prepared iron nanoparticles were examined by TEM. The images revealed nearly spherical and monodisperse nature of nanoparticle with minimum agglomeration (Fig. 4). This indicates the successful formation and stabilization of iron nanoparticles. This indicates that the phytoconstituents of *C. sativum* L leaves act as efficient reducing and capping agent. This was in consonance with earlier findings²¹.

The thermal behaviour of green synthesized FeONPs was investigated using differential scanning calorimeter. As shown in Figure 5, single endothermic peak was seen at 176.91°C. This might be due to desorption of water molecules from the surface of iron nanoparticles. Recently, Lakshminarayanan *et al.*, 2021²², also reported endothermic peak at 180°C. The absence of any other exothermic or endothermic peak

clearly indicates thermal stability of green synthesized nanoparticles. Hence, phytoconstituents present in aqueous extract of *C. sativum* L. efficiently reduced and stabilized FeONPs.

A vibrating sample magnetometer (VSM) was used to measure the magnetic properties of prepared iron nanoparticles. Thus, the magnetometry of the formed nanoparticles was measured at room temperature in the -16,000 to 16,000 O_e (Oersted) magnetic field. The saturation magnetization (M_s) of prepared FeONPs was 3.483 emu/g while the remnant magnetization (M_r) was 45.389 emu/g and the coercivity (C_e) value was 62.969G. The disappearance of hysteresis loop in (Fig. 6), revealed the superparamagnetic nature of green synthesized FeONPs. It also indicates the absence of long-range magnetic dipole-dipole interaction among the assemblies of superparamagnetic NPs.

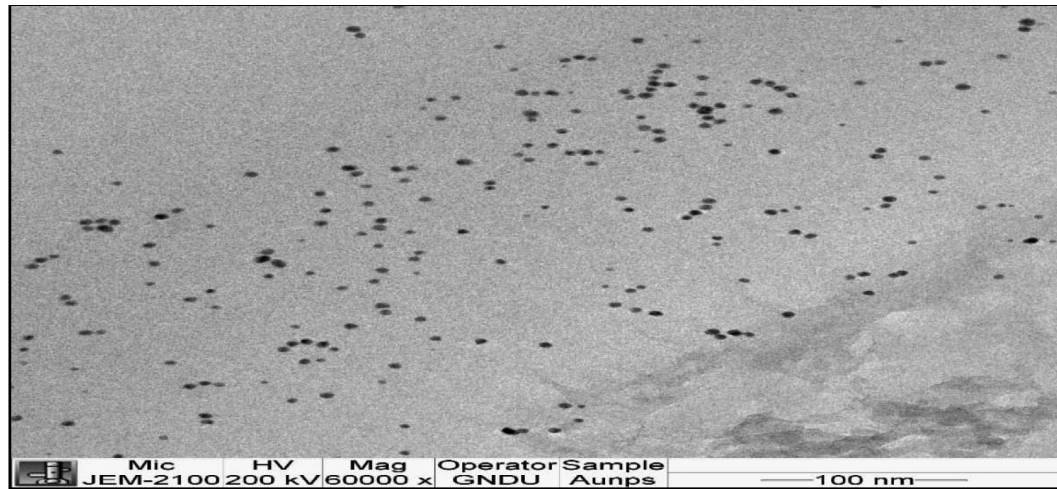


Fig. 4 — Transmission electron micrograph of iron oxide nanoparticles at a magnification of 150000 X

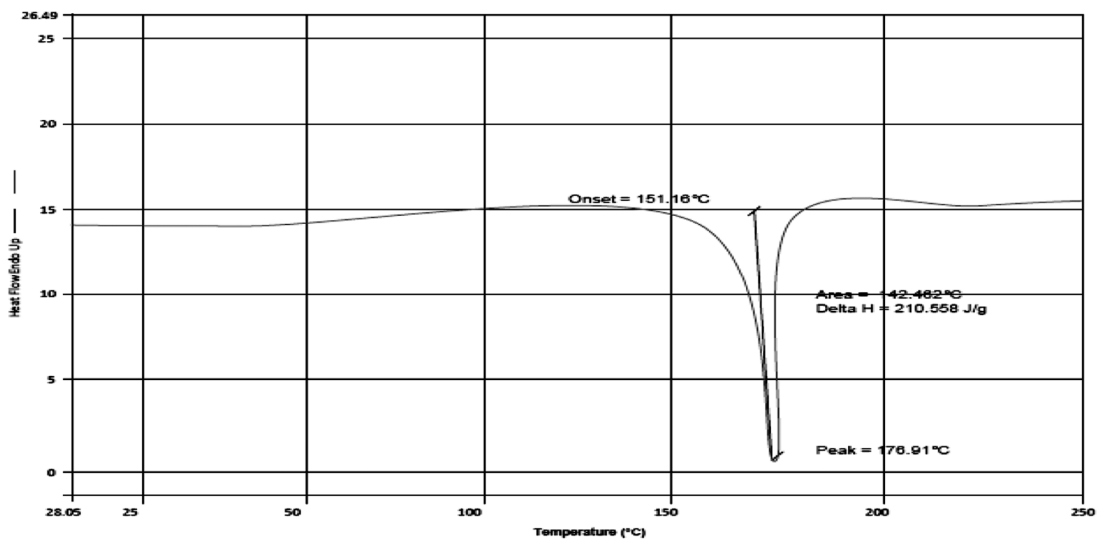


Fig. 5 — DSC curves of iron oxide nanoparticles obtained from aqueous extract of *C. sativum* L.

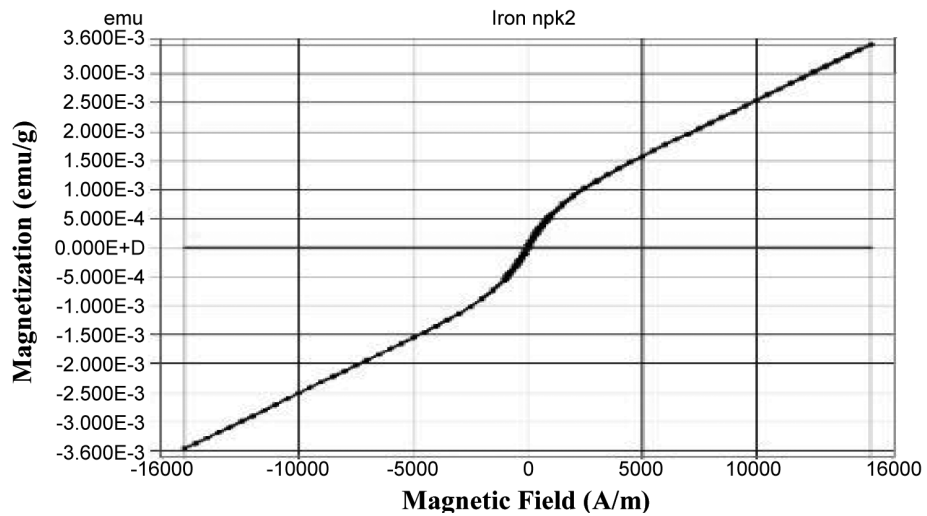


Fig. 6 — Magnetization of green synthesized iron oxide nanoparticles against applied magnetic field

However, the sigmoidal shape of the graph indicates presence of nanostructures with small magnetic fields. The magnetic measurements of the green synthesized FeONPs were similar to the work reported by Mamani *et al.*, 2014 and Andrade *et al.*, 2020^{23,24}.

Conclusion

FeONPs was successfully synthesized using a green synthesis technique with *Coriandrum sativum* L. leaf extract. *C. sativum* leaf extracts with strong antioxidant capacity. The polyphenols like quercetin present in leaf extract act as both reducing and capping agents for the nanoparticles thus producing discrete iron nanoparticles. The approach used is safe, sustainable and cost-effective for large-scale production of iron nanoparticles.

Conflict of interest

All authors declare no conflict of interest.

References

- Darezereshki E, Ranjbar M & Bakhtiari F, One-step synthesis of maghemite (γ -Fe₂O₃) nano-particles by wet chemical method. *J Alloys Compd*, 502 (2010) 257.
- Saratale R, Karuppusamy I, Saratale G, Pugazhendhi A, Kumar G & Park Y, A comprehensive review on green nanomaterials using biological systems: recent perception and their future applications. *Colloids Surf B: Biointerfaces*, 170 (2018) 20.
- Muthukumar H, Chandrasekaran NI, Mohammed SN, Pichiah S & Manickam M, Iron oxide nano-material: physicochemical traits and *in vitro* antibacterial propensity against multidrug resistant bacteria. *J Ind Eng Chem*, 45 (2017) 121.
- Deepika H, Jacob L & Rajender NN, A greener synthesis of core (Fe, Cu)-Shell (Au, Pt, Pd, and Ag) nanocrystals using aqueous vitamin C. *ACS Sustainable Chem Eng*, 1 (2013) 703.
- OscarLF, Vismaya S, Arunkumar M, Thajuddin N, Dhanasekaran D & Nithya C, Algal nanoparticles: Synthesis and biotechnological potentials. In: *Algae- Organisms for Imminent Biotechnology* (Ed. by N Thajuddin & D Dhanasekaran, Open Access Peer-reviewed edited volume), 2016.
- Baker S, Rakshith D, Kavitha KS, Santosh P, Kavitha HU, Rao Y & Satish S, Plants: emerging as nano factories towards facile route in synthesis of nanoparticles. *Bioimpacts*, 3 (2013) 111.
- Makarov VV, Makarova SS, Love AJ, Sinitsyna OV, Dudnik AO, Yaminsky IV, Taliansky ME & Kalinina NO, Biosynthesis of stable iron oxide nanoparticles in aqueous extracts of *Hordeum vulgare* and *Rumex acetosa* plants. *Langmuir*, 30 (2014) 5982.
- Kamaraj M, Kidane T, Muluken KU & Aravind J, Bio fabrication of iron oxide nanoparticles as a potential photocatalyst for dye degradation with antimicrobial activity. *Int J Environ Sci Technol*, 16 (2019) 8305.
- Bishnoi S, Kumar A & Selvaraj R, Facile synthesis of magnetic iron oxide nanoparticles using inedible *Cynometra ramiflora* fruit extract waste and their photocatalytic degradation of methylene blue dye. *Mater Res Bull*, 97 (2018) 121.
- Karpagavinayagam P & Vedhi C, Green synthesis of iron oxide nanoparticles using *Avicennia marina* flower extract. *Vacuum*, 160 (2019) 286.
- Bibi I, Nazar N, Ata S, Sultan M, Ali A, Abbas A, Jilani K, Kamal S, Sarim FM, Khan MI, Jalal F & Iqbal M, Green synthesis of iron oxide nanoparticles using pomegranate seeds extract and photocatalytic activity evaluation for the degradation of textile dye. *J Mater Res Technol*, 8 (2019) 6115.
- Singh K, Chopra DS, Singh D & Singh N, Optimization and ecofriendly synthesis of iron oxide nanoparticles as potential antioxidant. *Arab J Chem*, 13 (2020) 9034.
- Singh K, Chopra DS, Singh D & Singh N, Development of a validated high-performance thin-layer chromatography method for standardization of aqueous extract from the leaf of *Coriandrum sativum* L. *J Planar Chromat*, 34 (2021) 337.
- Arokiyaraj S, Saravanan M, Prakash NKU, Arasu MV, Vijayakumar B & Vincent, S, Enhanced antibacterial activity of iron oxide magnetic nanoparticles treated with *Argemone excicana* L. leaf extract: an *in vitro* study. *Mater Res Bull*, 48 (2013) 3323.
- Saranya S, Vijayarani K & Pavithra S, Green synthesis of iron nanoparticles using aqueous extract of *Musa ornate* flower sheath against pathogenic bacteria. *Indian J Pharm Sci*, 79 (2017) 688.
- Devatha C, Thalla AK & Katte SY, Green synthesis of iron nanoparticles using different leaf extracts for treatment of domestic waste water. *J Clean Prod*, 139 (2016) 1425.
- Awwad AM & Salem NM, A green and facile approach for synthesis of magnetite nanoparticles. *Nanosci Nanotechnol*, 2 (2012) 208.
- Shi SF, Jia JF, Guo XF, Zhao YP, Chen DS & Guo YY, Biocompatibility of chitosan-coated iron oxide nanoparticles with osteoblast cells. *Int J Nanomed*, 7 (2012) 5593.
- Bhattacharjee S, DLS and zeta potential – What they are and what they are not? *J Control Release*, 235 (2016) 337.
- Igwe OU & Nwamezie F, Green synthesis of iron nanoparticles using flower extract of *Piliostigma thonningii* and antibacterial activity evaluation. *Chem Int*, 4 (2018) 60.
- Prasad KS, Gandhi P & Selvaraj K, Synthesis of green nano iron particles (GnIP) and their application in adsorptive removal of As (III) and As (V) from aqueous solution. *Appl Surf Sci*, 317 (2014) 1052.
- Lakshminarayanan S, Shereen MF & Niraimathi KL, One-pot green synthesis of iron oxide nanoparticles from *Bauhinia tomentosa*: Characterization and application towards synthesis of 1, 3 diolein. *Sci Rep*, 11 (2021) 8643.
- Mamani JB, Gamarra LF & Brit GE, Synthesis and characterization of Fe₃O₄ nanoparticles with perspectives in biomedical applications. *Mater Res*, 17 (2014) 542.
- Andrade RGD, Veloso SRS, Castanheira EMS. Shape anisotropic iron oxide-based magnetic nanoparticles: Synthesis and biomedical applications. *Int J Mol Sci*, 21 (2020) 2455.